

Triplet Pairing Superconductivity Induced by Short-Range Ferromagnetic Correlations in Sr_2RuO_4

Kengo HOSHIHARA and Kazumasa MIYAKE

*Division of Materials Physics, Department of Materials Engineering Science,
Graduate School of Engineering Science, Osaka University, Toyonaka 560-8531*

(Received February 2, 2008)

The microscopic origin of triplet superconductivity in Sr_2RuO_4 is discussed, paying attention to the role of Coulomb interaction, U_{pp} , at the O site. It is shown on the d - p model that U_{pp} induces a ferromagnetic exchange interaction between "d-electrons" (molecular orbital with d_{xy} -symmetry) at adjacent Ru sites, leading to short-range ferromagnetic correlations and promoting Cooper pairing with $(\sin p_x \pm i \sin p_y)$ -symmetry on the γ -band. The reason why such ferromagnetic correlations work effectively may be traced back to the fact that the level of $4d$ -electrons at Ru sites is relatively low and located near that of $2p$ -electrons at O sites.

KEYWORDS: Sr_2RuO_4 , superconductivity, ferromagnetic correlations, second-order perturbation

Since its discovery by Maeno *et al.*,¹ superconductivity in Sr_2RuO_4 has attracted much attention both experimentally and theoretically. Now it seems to have been established experimentally that the superconducting (SC) state is in the chiral spin triplet state.^{2,3} The existence of technically linelike nodes in the SC gap has also been suggested.⁴⁻⁶ Since these observations are in contrast with the expectation at the early stage of theoretical works,^{7,8} some phenomenological gap models have been proposed to explain those experiments.⁹⁻¹¹ The results of ref. 9 were consistent with the observed gap with linelike nodes in [100] and [010] directions.¹² On the other hand, microscopic calculations have been performed on various models and methods.¹³⁻¹⁶ The results on the multiband Hubbard model by Nomura and Yamada¹⁵ seem consistent with almost all the available measurements to date probing the gap structure. However, the Hubbard model with only on-site repulsion, U_{dd} , seems too stoical to discuss the superconductivity in Sr_2RuO_4 because the quasi-particles (QP) consist of $4d$ -electrons at Ru sites and $2p$ -ones at O sites. Then the intersite interaction between QP, arising through the Coulomb interaction at O sites, may not be neglected, while the direct Coulomb interaction V between $4d$ -electrons at the nearest-neighbor Ru sites¹⁷ would be negligibly small. The interaction overlooked so far is

$$\mathcal{H}_{\text{ex}} = -\frac{U_{pp}}{6} \sum_{m,i} \sum_{\alpha\beta\gamma\delta} p_{mi\alpha}^\dagger p_{mi\gamma}^\dagger p_{mi\delta} p_{mi\beta} (\vec{\sigma}_{\alpha\beta} \cdot \vec{\sigma}_{\gamma\delta}), \quad (1)$$

where $p_{mi\sigma}$ is the operator for a $2p_m$ -electron ($m = x, y$) of spin σ at the i th site, and $\vec{\sigma}_{\alpha\beta}$'s are the Pauli matrices. Such a Coulomb interaction gives rise to an effective intersite correlation J between the molecular orbital with d_{xy} -symmetry ("d-electron"). We expect that eq. (1) can be expressed phenomenologically as

$$\mathcal{H}_{\text{ex}} \simeq - \sum_{\mathbf{k}\mathbf{k}'\mathbf{q}} \sum_{\alpha\beta\gamma\delta} J_{\mathbf{q}} \tilde{d}_{\mathbf{k}+\mathbf{q}\alpha}^\dagger \tilde{d}_{\mathbf{k}'-\mathbf{q}\gamma}^\dagger \tilde{d}_{\mathbf{k}'\delta} \tilde{d}_{\mathbf{k}\beta} (\vec{\sigma}_{\alpha\beta} \cdot \vec{\sigma}_{\gamma\delta}), \quad (2)$$

where $\tilde{d}$ denotes the operator for a "d-electron" and $J_{\mathbf{q}} = 2J(\cos q_x + \cos q_y)$. Although exchange interaction (2) is a too simplified version, we derive a more realistic and complicated version later starting with the d - p model and show that this kind of intersite interaction promotes short-range ferromagnetic correlations (SRFMCs), which have been measured quite recently by inelastic neutron scattering.¹⁸ The purpose of this Letter is to demonstrate that SRFMC promotes triplet pairing with $(\sin p_x \pm i \sin p_y)$ -symmetry, as proposed in ref. 9. We follow the weak-coupling calculations with the pairing interaction given by the second-order perturbation theory (SOPT) with respect to U_{dd} and U_{pp} .

Let us consider the situation drawn in Fig. 1, where a $2p_x$ - or $2p_y$ -orbital is sandwiched between two d -orbitals with d_{xy} -symmetry. Hereafter, we restrict our discussion within the

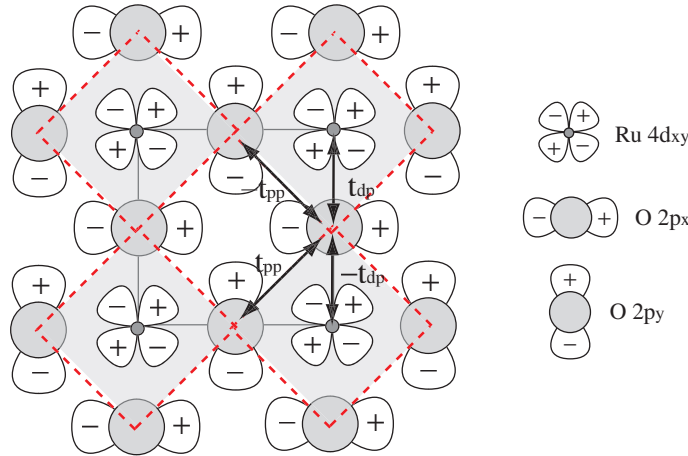


Fig. 1. Schematic figure of RuO_2 plane. t_{dp} and t_{pp} are hopping integrals. Gray domains circled by dashed squares represent the molecular orbitals, which form a two-dimensional square lattice.

γ -band since it is expected to provide the main contribution.¹⁵ The noninteracting d - p Hamiltonian, which can well describe the situation shown in Fig. 1, is given as follows:

$$\mathcal{H}_{dp}^{(0)} = \sum_{\mathbf{k},\sigma} \begin{pmatrix} d_{\mathbf{k}\sigma}^\dagger & p_{x\mathbf{k}\sigma}^\dagger & p_{y\mathbf{k}\sigma}^\dagger \end{pmatrix} \begin{pmatrix} \varepsilon_d & V_{y\mathbf{k}}^* & V_{x\mathbf{k}}^* \\ V_{y\mathbf{k}} & \varepsilon_p & W_{\mathbf{k}} \\ V_{x\mathbf{k}} & W_{\mathbf{k}} & \varepsilon_p \end{pmatrix} \begin{pmatrix} d_{\mathbf{k}\sigma} \\ p_{x\mathbf{k}\sigma} \\ p_{y\mathbf{k}\sigma} \end{pmatrix} \equiv \sum_{\mathbf{k},\sigma} \vec{\phi}_{\mathbf{k}\sigma}^\dagger \hat{\mathcal{H}}_{\mathbf{k}}^{(0)} \vec{\phi}_{\mathbf{k}\sigma}, \quad (3)$$

where $d_{\mathbf{k}\sigma}$ and $p_{m\mathbf{k}\sigma}$ are the operators for $4d$ - and $2p_m$ -electrons of momentum $\mathbf{k}$ and spin

σ , respectively, $V_{m\mathbf{k}} = 2it_{dp}\sin(\frac{k_m}{2})$, and $W_{\mathbf{k}} = 4t_{pp}\sin(\frac{k_x}{2})\sin(\frac{k_y}{2})$. Note that we should take $t_{pp} < 0$ for discussing Sr_2RuO_4 , while $t_{pp} > 0$ for the cuprates. Solving the equation $\det(\hat{\mathcal{H}}_{\mathbf{k}}^{(0)} - \lambda_{\mathbf{k}}\hat{1}) = 0$, we can obtain the eigenvalue $\lambda_{i\mathbf{k}}$ and eigenvector $\vec{u}_{i\mathbf{k}}$ ($i = 1, 2, 3$). Then, the diagonalized Hamiltonian becomes

$$\mathcal{H}_{dp}^{(0)} = \sum_{\mathbf{k}, \sigma} \vec{\psi}_{\mathbf{k}\sigma}^\dagger \hat{\mathcal{H}}_{\mathbf{k}}^D \vec{\psi}_{\mathbf{k}\sigma}. \quad (4)$$

Here, $\vec{\phi}_{\mathbf{k}\sigma}$ is related to $\vec{\psi}_{\mathbf{k}\sigma}$ by the relation $\vec{\phi}_{\mathbf{k}\sigma} = \hat{U}_{\mathbf{k}}^{-1} \vec{\psi}_{\mathbf{k}\sigma}$, where the matrix $\hat{U}_{\mathbf{k}}$ is defined as $\hat{U}_{\mathbf{k}} = (\vec{u}_{1\mathbf{k}} \ \vec{u}_{2\mathbf{k}} \ \vec{u}_{3\mathbf{k}})$. Substituting the relations between $\vec{\phi}_{\mathbf{k}\sigma}$ and $\vec{\psi}_{\mathbf{k}\sigma}$ into eq. (1), we obtain, as shown below, the effective interaction between QP described by $a_{i\mathbf{k}\sigma}$. For this purpose, it is enough to confine our discussions within the case $t_{pp} = 0$: namely we need not consider the hopping t_{pp} . Because electrons located on both sides of a certain O site can interact with each other effectively only through the O site, the term including t_{pp} corresponds to the next nearest-neighbor interaction (higher-order contribution). Then, hereafter, we can use simplified relations such as

$$d_{\mathbf{k}\sigma} = \frac{\lambda_{1\mathbf{k}}}{L_{1\mathbf{k}}} a_{1\mathbf{k}\sigma} + \frac{\lambda_{2\mathbf{k}}}{L_{2\mathbf{k}}} a_{2\mathbf{k}\sigma} + \frac{\lambda_{3\mathbf{k}}}{L_{3\mathbf{k}}} a_{3\mathbf{k}\sigma}, \quad (5)$$

$$p_{m\mathbf{k}\sigma} = \frac{V_{m\mathbf{k}}}{L_{1\mathbf{k}}} a_{1\mathbf{k}\sigma} + \frac{V_{m\mathbf{k}}}{L_{2\mathbf{k}}} a_{2\mathbf{k}\sigma} + \frac{V_{m\mathbf{k}}}{L_{3\mathbf{k}}} a_{3\mathbf{k}\sigma}, \quad (6)$$

where $L_{i\mathbf{k}} = (|V_{x\mathbf{k}}|^2 + |V_{y\mathbf{k}}|^2 + \lambda_{i\mathbf{k}}^2)^{1/2}$ ($i = 1, 2, 3$). Moreover, it is sufficient to consider only the QP on the orbital $i = 1$, because the other bands are completely filled with electrons. Hereafter, we denote $a_{1\mathbf{k}\sigma}$ and $L_{1\mathbf{k}}$ simply as $a_{\mathbf{k}\sigma}$ and $L_{\mathbf{k}}$, respectively. The operator $a_{\mathbf{k}\sigma}$ is regarded as the $\tilde{d}_{\mathbf{k}\sigma}$ in eq. (2).

Now we introduce the interaction terms. Using relations (5) and (6), we express such terms using $a_{\mathbf{k}\sigma}$'s. Substituting relation (6), into the Fourier transformed form of eq. (1), we obtain

$$\mathcal{H}_{\text{ex}}^{(x)} = -\frac{U_{pp}}{6} \sum_{\mathbf{k}\mathbf{k}'\mathbf{q}} \sum_{\alpha\beta\gamma\delta} \frac{V_{x\mathbf{k}+\mathbf{q}} V_{x\mathbf{k}'-\mathbf{q}} V_{x\mathbf{k}'} V_{x\mathbf{k}}}{L_{\mathbf{k}+\mathbf{q}} L_{\mathbf{k}'-\mathbf{q}} L_{\mathbf{k}'} L_{\mathbf{k}}} a_{\mathbf{k}+\mathbf{q}\alpha}^\dagger a_{\mathbf{k}'-\mathbf{q}\gamma}^\dagger a_{\mathbf{k}'\delta} a_{\mathbf{k}\beta} (\vec{\sigma}_{\alpha\beta} \cdot \vec{\sigma}_{\gamma\delta}). \quad (7)$$

At first sight, it seems that this interaction Hamiltonian, eq. (7), has a complicated form in real space. However, if we neglect the $\mathbf{k}$ -dependence of $L_{\mathbf{k}}$'s where $L_{\mathbf{k}} \equiv \Delta \sim O(\varepsilon_d - \varepsilon_p)$, we can perform the Fourier transformation of eq. (7), leading to

$$\begin{aligned} \mathcal{H}_{\text{ex}} = & \frac{-U_{pp}t_{dp}^4}{3\Delta^4} \sum_{\langle i,j \rangle} \sum_{\alpha\beta\gamma\delta} \{ (i, i, i, i) + (i, j, j, i) \\ & + (i, j, i, j) + (i, i, j, j) - (i, i, i, j) - (i, i, j, i) \\ & - (j, i, i, i) - (i, j, i, i) \} (\vec{\sigma}_{\alpha\beta} \cdot \vec{\sigma}_{\gamma\delta}), \end{aligned} \quad (8)$$

where we have added the term arising from the exchange process along the y -direction, the sum $\langle i, j \rangle$ is taken within the nearest-neighbor sites, and the abbreviation (i, j, k, l) represents the term $a_{i\alpha}^\dagger a_{j\gamma}^\dagger a_{k\delta} a_{l\beta}$. Eventually, it is revealed that eq. (7) contains all the types of interaction

between two electrons at nearest-neighbor Ru sites. Performing the Fourier transformation again and executing straightforward calculations, we can rewrite eq. (8) into the following form:

$$\mathcal{H}_{\text{ex}} = -\frac{1}{4} \sum_{\mathbf{k}\mathbf{k}'\mathbf{q}} \sum_{\alpha\beta\gamma\delta} J_{\mathbf{k},\mathbf{k}';\mathbf{q}} a_{\mathbf{k}+\mathbf{q}\alpha}^\dagger a_{\mathbf{k}'-\mathbf{q}\gamma}^\dagger a_{\mathbf{k}'\delta} a_{\mathbf{k}\beta} (\vec{\sigma}_{\alpha\beta} \cdot \vec{\sigma}_{\gamma\delta} - \delta_{\alpha\beta} \delta_{\gamma\delta}), \quad (9)$$

$$J_{\mathbf{k},\mathbf{k}';\mathbf{q}} = \frac{2U_{pp}t_{dp}^4}{L_{\mathbf{k}+\mathbf{q}}L_{\mathbf{k}'-\mathbf{q}}L_{\mathbf{k}'}L_{\mathbf{k}}} \sum_m \left\{ \frac{1}{2} + \cos q_m - \cos k_m - \cos k'_m + \frac{1}{2} \cos(k_m + k'_m) \right\}. \quad (10)$$

In eq. (10), the $\mathbf{k}$ -dependence of $L_{\mathbf{k}}$'s is recovered again. The second term in the curly brackets of eq. (10), $\cos q_m$, corresponds to the simplified version of eq. (2). There are many terms which are not included in the naive estimation, eq. (2). Therefore, the coupling constant J cannot be written simply as $J_{\mathbf{q}}$, but has a complicated momentum dependence $J_{\mathbf{k},\mathbf{k}';\mathbf{q}}$ as eq. (10). The term $\delta_{\alpha\beta}\delta_{\gamma\delta}$ in eq. (9), which appears automatically through the procedure above, assures that, due to the Pauli principle, there is no interaction between electrons with the parallel spin direction originally on the same O site. For interaction (9) to play an important role, the

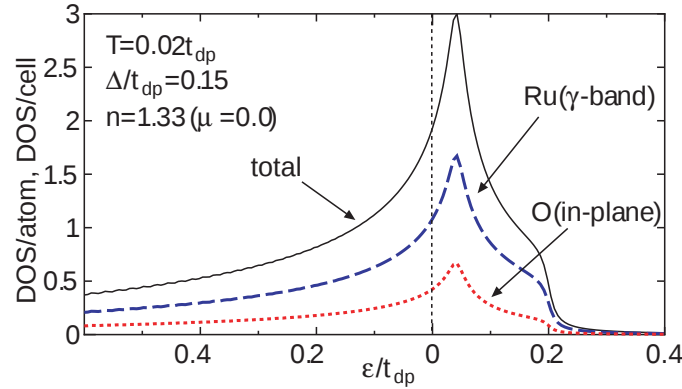


Fig. 2. Total and partial DOS in RuO_2 plane.

ratio $t_{dp}/(\varepsilon_d - \varepsilon_p) \equiv t_{dp}/\Delta$ should not be too small (namely, Δ/t_{dp} should not be too large). Such a condition is expected to be fulfilled in Ru-oxides because the level of $4d$ -electrons in Ru is deeper than that of $3d$ -electrons in Fe or of $5d$ -electrons in Os in general, and the level is located near that of $2p$ -electrons at the O site. This implies that there exists a strong hybridization between Ru and O. Indeed, as shown in Fig. 2, the partial density of states (DOS) for $4d_{xy}$, $2p_x$ and $2p_y$ obtained by band structure calculations^{19,20} are reproduced by taking $\Delta/t_{dp} \simeq 0.15$ with the use of eqs. (5) and (6): namely, $\rho_\gamma \simeq 2.0\rho_O$ ($\rho_\gamma \simeq 0.5\rho_{\text{Ru}}$) where ρ_γ , ρ_{Ru} and ρ_O denote the partial DOS per atom (at the Fermi level) of Ru (γ -band), Ru (total of α -, β -, and γ -bands) and O (in-plane), respectively. The same procedure is applicable to the on-site Coulomb repulsion U_{dd} between d -electrons, $U_{dd} \sum_i d_{i\uparrow}^\dagger d_{i\uparrow} d_{i\downarrow}^\dagger d_{i\downarrow}$. Along the way

parallel to obtaining exchange interaction (7) from the original interaction between p -electrons, eq. (1), the Hubbard interaction is expressed in terms of the $a_{\mathbf{k}\sigma}$ operators describing the QP band. Then, the total Hamiltonian is given by

$$\mathcal{H} = \sum_{\mathbf{k},\sigma} (\lambda_{\mathbf{k}} - \mu) a_{\mathbf{k}\sigma}^\dagger a_{\mathbf{k}\sigma} + \sum_{\mathbf{k}\mathbf{k}'\mathbf{q}} U_{\mathbf{k},\mathbf{k}';\mathbf{q}} a_{\mathbf{k}+\mathbf{q}\uparrow}^\dagger a_{\mathbf{k}'-\mathbf{q}\downarrow}^\dagger a_{\mathbf{k}'\downarrow} a_{\mathbf{k}\uparrow} + \mathcal{H}_{\text{ex}}, \quad (11)$$

$$U_{\mathbf{k},\mathbf{k}';\mathbf{q}} = \frac{U_{dd} \lambda_{\mathbf{k}+\mathbf{q}} \lambda_{\mathbf{k}'-\mathbf{q}} \lambda_{\mathbf{k}'} \lambda_{\mathbf{k}}}{8L_{\mathbf{k}+\mathbf{q}} L_{\mathbf{k}'-\mathbf{q}} L_{\mathbf{k}'} L_{\mathbf{k}}}, \quad (12)$$

where μ denotes the chemical potential. It is noted that the repulsion U_{dd} in eq. (12) should be regarded as an effective interaction between QP, that is reduced by the electron correlation leaving a relatively heavy QP. We set $t_{pp} = -0.4t_{dp}$ to reproduce the Fermi surface of the γ -band given by the band structure calculations. Then the bandwidth of the γ -band is $W \sim 2.2t_{dp}$. The last two terms of eq. (11) can be rewritten into a more convenient form to perform the perturbation expansion as follows:

$$\mathcal{H}_{\text{int}} = \sum_{\mathbf{k}\mathbf{k}'\mathbf{q}} \tilde{J}_{\mathbf{k},\mathbf{k}';\mathbf{q}} a_{\mathbf{k}+\mathbf{q}\uparrow}^\dagger a_{\mathbf{k}'-\mathbf{q}\downarrow}^\dagger a_{\mathbf{k}'\downarrow} a_{\mathbf{k}\uparrow}, \quad (13)$$

$$\tilde{J}_{\mathbf{k},\mathbf{k}';\mathbf{q}} = U_{\mathbf{k},\mathbf{k}';\mathbf{q}} + J_{\mathbf{k},\mathbf{k}';\mathbf{q}} + J_{\mathbf{k}',\mathbf{k};\mathbf{k}-\mathbf{k}'+\mathbf{q}}. \quad (14)$$

Hereafter, t_{dp} is adopted as a unit of energy.

The static spin susceptibility $\chi_{\perp}(\mathbf{k}, 0)$ including vertex correction, up to the first-order perturbation, is given by

$$\chi_{\perp}(\mathbf{q}, i\omega) = -T \sum_{\varepsilon, \mathbf{p}} \left\{ 1 - T \sum_{\varepsilon', \mathbf{p}'} \tilde{J}_{\mathbf{p}+\mathbf{q}, \mathbf{p}'; -\mathbf{p}+\mathbf{p}'} \mathcal{G}(\mathbf{p}' + \mathbf{q}, i\vare' + i\omega) \mathcal{G}(\mathbf{p}', i\vare) \right\} \mathcal{G}(\mathbf{p} + \mathbf{q}, i\vare + i\omega) \mathcal{G}(\mathbf{p}, i\vare), \quad (15)$$

whose diagrammatic expression is shown in Fig. 3(b). It is enough to calculate $\chi_{\perp}$ because the SU(2) symmetry is preserved. The results of numerical calculations are shown in Fig. 4.

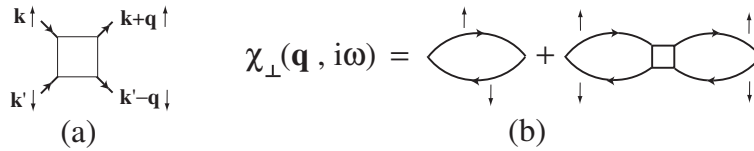


Fig. 3. (a) Vertex $\tilde{J}_{\mathbf{k},\mathbf{k}';\mathbf{q}}$. (b) Spin susceptibility $\chi_{\perp}(\mathbf{q}, i\omega)$.

$\chi_{\perp}(\mathbf{q}, 0)$ has some peaks at some incommensurate wave vectors $\mathbf{Q}_{\text{ic}}$'s. The Fermi surface simulating the γ -band of Sr_2RuO_4 has no nesting tendency, although the Fermi surface shifted by $\mathbf{Q}_{\text{ic}}$'s has a point contact in the extended Brillouin zone scheme.²¹ Therefore, the peak structure of $\chi_{\perp}(\mathbf{q}, 0)$ at $\mathbf{Q}_{\text{ic}}$'s is considered to come from the band effect. In particular, the shape of $\chi_{\perp}(\mathbf{q}, 0)$ consists of a broad peak around $\mathbf{q} = (0, 0)$ and a small dip (at $\mathbf{q} \sim (0, 0)$),

which gives rise to a practical SRFMC. The effect of U_{dd} is to enhance $\chi_{\perp}(\mathbf{q}, 0)$ in the entire $\mathbf{q}$ -space as seen in Fig. 4. On the other hand, the peak around $\mathbf{q} = (0, 0)$ is much more enhanced by U_{pp} than by U_{dd} , while there is no extra increase by U_{pp} at (π, π) . The qualitative behavior of $\chi_{\perp}(\mathbf{q}, 0)$ remains unchanged if we neglect the $\mathbf{k}$ -dependence of $L_{\mathbf{k}}$'s in eq. (10) or (12). Then, we can draw the picture that SRFMC is induced by the effect of on-site repulsion between p -electrons at the O site. The broad peak structure at $\mathbf{q} = (0, 0)$ is consistent with

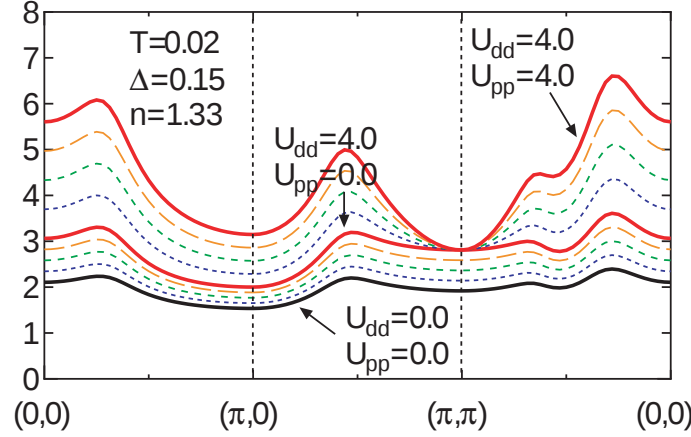


Fig. 4. Momentum dependence of static spin susceptibility $\chi_{\perp}(\mathbf{q}, 0)$ for several values of U_{dd} and U_{pp} . The dashed lines that have no parameter values correspond to, from the lower line, $(U_{dd}, U_{pp}) = (1, 0), (2, 0)$ and so on, respectively. Namely, we first applied U_{dd} , then applied U_{pp} .

the SRFMC that has been measured quite recently by inelastic neutron scattering,¹⁸ and is responsible for the occurrence of triplet superconductivity in Sr_2RuO_4 as discussed below. As for the results of different electron fillings, the more electrons are doped, the more the peak structure around $\mathbf{q} = (0, 0)$ is enhanced.

Diagrams for the irreducible pairing vertices up to SOPT in terms of $\tilde{J}$ are shown in Fig. 5. Its analytic expressions are given as follows:

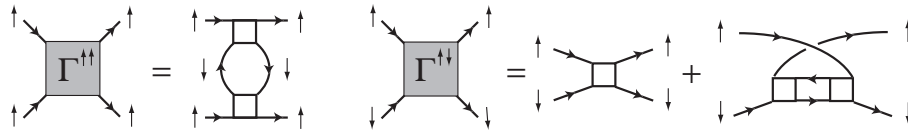


Fig. 5. Pairing interaction vertices $\Gamma^{\uparrow\uparrow}$ and $\Gamma^{\uparrow\downarrow}$ up to the second-order perturbation with respect to $\tilde{J}$. The solid line and the square denote the noninteracting Matsubara Green function $\mathcal{G}$ and the intersite coupling vertex $\tilde{J}$, respectively.

$$\Gamma_{\mathbf{k}, \mathbf{k}'}^{\uparrow\uparrow} = T \sum_{\varepsilon, \mathbf{p}} \tilde{J}_{\mathbf{k}, \mathbf{p}; -\mathbf{k}+\mathbf{k}'} \tilde{J}_{\mathbf{p}+\mathbf{k}-\mathbf{k}', -\mathbf{k}; -\mathbf{k}+\mathbf{k}'} \mathcal{G}(\mathbf{p}, i\varepsilon) \mathcal{G}(\mathbf{p} + \mathbf{k} - \mathbf{k}', i\varepsilon), \quad (16)$$

$$\Gamma_{\mathbf{k},\mathbf{k}'}^{\uparrow\downarrow} = \tilde{J}_{\mathbf{k},-\mathbf{k};-\mathbf{k}+\mathbf{k}'} - T \sum_{\varepsilon,\mathbf{p}} \tilde{J}_{\mathbf{k},\mathbf{p};\mathbf{p}+\mathbf{k}'} \tilde{J}_{-\mathbf{k},\mathbf{p}+\mathbf{k}+\mathbf{k}';\mathbf{p}+\mathbf{k}} \mathcal{G}(\mathbf{p}, i\varepsilon) \mathcal{G}(\mathbf{p} + \mathbf{k} + \mathbf{k}', i\varepsilon). \quad (17)$$

The pairing interaction in the triplet manifold, $V_{\mathbf{k}\mathbf{k}'}^t$, is given by eq. (16) directly, and that in the singlet manifold, $V_{\mathbf{k}\mathbf{k}'}^s$, is given by

$$V_{\mathbf{k},\mathbf{k}'}^s = \tilde{J}_{\mathbf{k},-\mathbf{k};-\mathbf{k}+\mathbf{k}'} - T \sum_{\varepsilon,\mathbf{p}} \tilde{J}_{\mathbf{k},\mathbf{p};\mathbf{p}-\mathbf{k}'} \tilde{J}_{-\mathbf{k},\mathbf{p}+\mathbf{k}-\mathbf{k}';\mathbf{p}+\mathbf{k}} \mathcal{G}(\mathbf{p}, i\varepsilon) \mathcal{G}(\mathbf{p} + \mathbf{k} - \mathbf{k}', i\varepsilon). \quad (18)$$

Note that SU(2) symmetry is preserved in the triplet manifold. Namely, the triplet component stemming from eq. (17) is the same as the one from eq. (16).

At $T = T_c$, we can use the linearized gap equation, in the weak-coupling formalism, given by

$$\Delta_{\mathbf{k}} = - \sum_{\mathbf{k}'} V_{\mathbf{k},\mathbf{k}'}^{s,t} \frac{\Delta_{\mathbf{k}'}}{\xi_{\mathbf{k}'}} \tanh\left(\frac{\xi_{\mathbf{k}'}}{2T_c}\right). \quad (19)$$

A proper way of obtaining the gap structure with the highest T_c is to solve eq. (19) as an eigenvalue problem without specifying the type of the gap $\Delta_{\mathbf{k}}$. However, for simplicity, we seek the variational solution for eq. (19). Namely, we calculate T_c by specifying the type of gap function, such as $\sqrt{2} \sin k_x$ (p_x -pairing), $\sqrt{2} \sin(k_x + k_y)$ (p_{x+y} -pairing) for triplet pairing, and $2 \sin k_x \sin k_y$ (d_{xy} -pairing), $[\cos k_x - \cos k_y]$ ($d_{x^2-y^2}$ -pairing) for singlet pairing. However, it is rational to consider that the type of pairing giving the highest T_c is dominant in the true gap function. The pairing interaction $V_{\mathbf{k},\mathbf{k}'}^t$, eq. (16), and $V_{\mathbf{k},\mathbf{k}'}^s$, eq. (18) is estimated at $T = 0.02$, because their values are not sensitive at temperatures $T < 0.02$. We adopt the first Brillouin zone divided into 45×45 $\mathbf{k}$ -meshes. The results for a series of parameters are shown in Fig. 6. We can see in Fig. 6 that T_c is enhanced as U_{pp} is applied. For a system with a fillings of $n = 1.33$, a small value of Δ (splitting between p - and d -levels), and a moderate value of U_{pp} , corresponding to Sr_2RuO_4 , p_x -pairing would be realized as shown in Fig. 6(a). When the system is located away from the half-filling state, it is also enhanced as shown in Fig. 6(b). On the other hand, p_{x+y} -pairing has T_c less than 10^{-3} . In ref. 17, it is discussed that the next nearest-neighbor (diagonal) pairings, d_{xy} - or p_{x+y} -pairing, are promoted due to the nearest-neighbor Coulomb repulsion V . In our case, on the contrary, the nearest-neighbor pairing, p_x -pairing, is realized through SRFMC of $\mathcal{H}_{\text{ex}}$. As for the other symmetries, $d_{x^2-y^2}$ and d_{xy} , we cannot obtain a finite T_c in the parameter region shown in Fig. 6. At first sight, it appears unrealistic that U_{pp} is larger than $U_{dd} \sim W$, because $3d$ -electrons are much more localized on the ion site than $2p$ -electrons. However, it is crucial to note that the Coulomb interactions here are effective ones that are greatly renormalized. Indeed, the effect of U_{pp} on QP cannot be screened by avoiding U_{pp} because QP consisting of molecular orbitals at the nearest-neighbor sites cannot get rid of U_{pp} . On the other hand, the effective interaction U_{dd} can be reduced by correlations and by making a heavy QP. Therefore the values adopted for

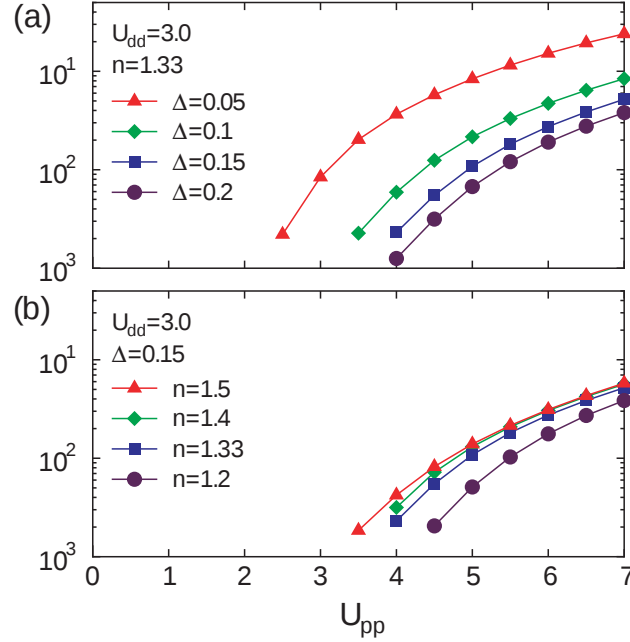


Fig. 6. T_c for triplet pairing with p_x -symmetry as a function of U_{pp} . (a) Δ dependence. (b) doping dependence.

U_{dd} and U_{pp} are considered to be not unrealistic.

In conclusion, we have derived from the so-called d - p model the effective intersite exchange interaction $\mathcal{H}_{\text{ex}}$, whose origin is the on-site Coulomb interaction at an O site. SRFMC were induced by this exchange interaction. Then, we have shown that the triplet SC state of $(\sin p_x \pm i \sin p_y)$ -symmetry is promoted as applying U_{pp} within SOPT. These results simulate quite well the properties observed in Sr_2RuO_4 . While our results are derived on SOPT for the pairing interaction, they might make sense at least in describing the qualitative behavior.²² It is possible to take into account the effect of α - and β -bands on the same footing as the γ -band since the exchange interaction arising from the same mechanism also works between QPs in these bands. According to preliminary calculations, the pairing with $[\sin(p_x + p_y) + i \sin(p_x - p_y)]$ -symmetry could be promoted, which is consistent with a line-node-like gap along the diagonal direction $k_x = \pm k_y$.^{12,15}

Acknowledgements

We have benefited much from conversations with H. Harima, H. Kohno and T. Takimoto. This work is supported by a Grant-in-Aid for Creative Scientific Research (No. 15GS0213), a Grant-in-Aid for Scientific Research (No. 16340103), and the 21st Century COE Program (G18) of the Japan Society for the Promotion of Science.

References

- 1) Y. Maeno, H. Hashimoto, K. Yoshida, S. Nishizaki, T. Fujita, J. G. Bednorz and F. Lichtenberg: Nature **372** (1994) 532.
- 2) G. M. Luke, Y. Fudamoto, K. M. Kojima, M. I. Larkin, J. Merrin, B. Nachumi, Y. J. Uemura, Y. Maeno, Z. Q. Mao, Y. Mori, H. Nakamura and M. Sigrist: Nature **394** (1998) 558.
- 3) K. Ishida, H. Mukuda, Y. Kitaoka, K. Asayama, Z. Q. Mao, Y. Mori and Y. Maeno: Nature **396** (1998) 658.
- 4) S. Nishizaki, Y. Maeno, S. Farner, S. Ikeda and T. Fujita: J. Phys. Soc. Jpn. **67** (1998) 560.
- 5) K. Ishida, H. Mukuda, Y. Kitaoka, Z. Q. Mao, Y. Mori and Y. Maeno: Phys. Rev. Lett. **84** (2000) 5387.
- 6) H. Mukuda, K. Ishida, Y. Kitaoka, K. Miyake, Z. Q. Mao, Y. Mori and Y. Maeno: Phys. Rev. B **65** (2002) 132507.
- 7) T. M. Rice and M. Sigrist: J. Phys. C **7** (1995) L643.
- 8) D. F. Agterberg, T. M. Rice and M. Sigrist: Phys. Rev. Lett. **78** (1997) 3374.
- 9) K. Miyake and O. Narikiyo: Phys. Rev. Lett. **83** (1999) 1423.
- 10) Y. Hasegawa, K. Machida and M. Ozaki: J. Phys. Soc. Jpn. **69** (2000) 336.
- 11) M. E. Zhitomirsky and T. M. Rice: Phys. Rev. Lett. **87** (2001) 057001.
- 12) K. Deguchi, Z. Q. Mao, H. Yaguchi and Y. Maeno: Phys. Rev. Lett. **92** (2004) 047002.
- 13) T. Takimoto: Phys. Rev. B **62** (2000) R14641.
- 14) T. Kuwabara and M. Ogata: Phys. Rev. Lett. **85** (2000) 4586.
- 15) T. Nomura and K. Yamada: J. Phys. Soc. Jpn. **71** (2002) 404.
- 16) K. Kuroki, Y. Tanaka, T. Kimura and R. Arita: Phys. Rev. B **69** (2004) 214511.
- 17) R. Arita, S. Onari, K. Kuroki and H. Aoki: Phys. Rev. Lett. **92** (2004) 247006.
- 18) M. Braden, Y. Sidis, P. Steffens, O. Friedt, P. Bourges, J. Kulda, S. Nakatsuji, N. Kikugawa and Y. Maeno: STRS2004, Kyoto, 25-28 October, 2004, **26P3**.
- 19) T. Oguchi: Phys. Rev. B **51** (1995) 1385.
- 20) D. J. Singh: Phys. Rev. B **52** (1995) 1358.
- 21) C. Bergemann, A. P. Mackenzie, S. R. Julian, D. Forsythe and E. Ohmichi: Adv. Phys. **52** (2003) 639.
- 22) J. Kondo: J. Phys. Soc. Jpn. **70** (2001) 808.